arXiv:cond-mat/0111180v1 [cond-mat.mtrl-sci] 9 Nov 2001

Tight-binding study of high-pressure phase transitions in titanium: alpha to omega and beyond

M. J. Mehl and D. A. Papaconstantopoulos
Center for Computational Materials Science, Naval Research Laboratory, Washington DC 20375-5000

(February 1, 2008)

We use a tight-binding total energy method, with parameters determined from a fit to first-principles calculations, to examine the newly discovered γ phase of titanium. Our parameters were adjusted to accurately describe the αTi-ωTi phase transition, which is misplaced by density functional calculations. We find a transition from ωTi to γTi at 102 GPa, in good agreement with the experimental value of 116 GPa. Our results suggest that current density functional calculations will not reproduce the ωTi-γTi phase transition, but will instead predict a transition from ωTi to the bcc βTi phase.

Structural transformations in titanium have received a great deal of experimental [1–4] and theoretical [5–10] attention. This Letter is motivated by a recent experimental study [1] which revealed a previously unsuspected phase transition in titanium at 116 GPa from the ωTi phase to a new γTi phase. We have been able to confirm these experiments by performing highly accurate tight-binding calculations of the phase diagram of Ti.

At room temperature the group-IV metals zirconium and hafnium transform under pressure from the ground state hexagonal close packed (hcp) phase to the intermediate pressure ω phase [2] (space group $P6/mmm-D^1_{6h}$, Pearson Symbol hP3, *Strukturbericht* Designation: C32) at 2.2 GPa [2] and 38 GPa [4], respectively. At 35 GPa [11,12] and 71 GPa [4], respectively, the metals transform from the ω phase to a body centered cubic (bcc) structure. One would logically assume that titanium also follows this transformation sequence, and indeed the transition from hcp αTi to ωTi takes place at a pressure variously given as 9 GPa [1] or 20-90 GPa [2]. However, no room temperature pressure driven transition from ωTi to βTi has been observed, although first-principles calculations predict a transition at 98 GPa, [5,10] and βTi exists at room pressure and temperatures above 1155 K. [13] Recently, however, Vohra and Spencer [1] found that at 116 GPa titanium transforms from the ω phase to a previously unsuspected γTi phase. The new phase has a two-atom body-centered orthorhombic unit cell, space group $Cmcm$–D^{17}_{2h}, Pearson symbol oC4, with the atoms at the points $(0, \pm yb, \pm c/4)$, where a, b, and c are the lengths of the primitive vectors in the full orthorhombic unit cell, and y is an internal parameter.

This crystal structure is observed in various materials, including αU, the random alloy AgCd, and a metastable form of gallium. [14] (The αU phase has the *Strukturbericht* designation A20. [15,16]) With appropriate choices of the parameters this structure can reproduce several higher symmetry phases. In particular, when $b/a = \sqrt{3}$ and $y = 1/6$, it becomes the hcp structure, while when $b/a = c/a = \sqrt{2}$ and $y = 1/4$ the atoms are on the sites of a bcc cell. Wentzcovitch and Cohen [17] used this pathway to describe a possible theoretical model for the hcp → bcc transition in magnesium.

Examination of the γTi structure by first-principles techniques requires a minimization of the total energy with respect to three parameters (*e.g.*, b/a, c/a, and y) at several volumes. This is impractical because of the high computational demand of first principles methods. We have instead chosen to study the α-ω-γ transformation sequence using the much faster NRL tight-binding method. [18,19] This method has been shown to reproduce the ground-state phase, elastic constants, surface energies, and vacancy formation energies of the transition metals. The tight-binding parameters in Ref. [19] were found by fitting to a Local Density Approximation (LDA) database of total energies and eigenvalues for the fcc and bcc structures. The parameters correctly predicted the ground state structures of all of the transition and noble metals, including the hcp metals and manganese. [20] However, upon examination, we found that the titanium parameters from Ref. [19] do not predict the correct position for the ωTi phase. In fact, no αTi-ωTi phase transition is seen.

We therefore developed a new set of tight-binding parameters according to the procedures of Ref. [19], fit to an expanded database of first-principles calculations. In particular, our database includes the fcc, bcc, simple cubic, hcp, and ω structures. The eigenvalues and total energies were generated using the general-potential Linearized Augmented Plane Wave (LAPW) method, [21,22] using the Perdew-Wang 1991 Generalized Gradient Approximation (GGA) [23,24] to density functional theory. We fit our tight-binding parameters to both total energies and band structures, using the parametrization described by equations (7), (8), (9), and (11) of Ref. [19]. The RMS error in fitting the energies for the lowest energy phases (hcp, ω, fcc, and bcc) was less than 1 mRy/atom. The band structure RMS error is about 10 mRy for the occupied bands of the hcp and ω structures. [25]

In agreement with previous calculations, [5–8] our first-principles results show that the ωTi phase is slightly lower in energy (about 0.5 mRy/atom) than αTi. This

TABLE I. The equilibrium lattice constants of the α (hcp), β (bcc), and ω phases of titanium, as determined by the tight-binding parameters described in the text, [25] the LAPW calculations used in the fitting procedure, and experiment. Note that βTi is not seen at room temperature. The lattice constant given is extrapolated from alloy data. [26] All values are in Bohr.

Phase	TB		LAPW		Exp.	
	a	c	a	c	a	c
α^{a}	5.561	8.609	5.547	8.779	5.575	8.851
β^{a}	6.118	6.118	6.137	6.137	6.206	6.206
ω^{b}	8.675	5.268	8.644	5.348	8.689	5.333

[a] Experimental data from Ref. [26]

[b] Experimental data from Ref. [1]

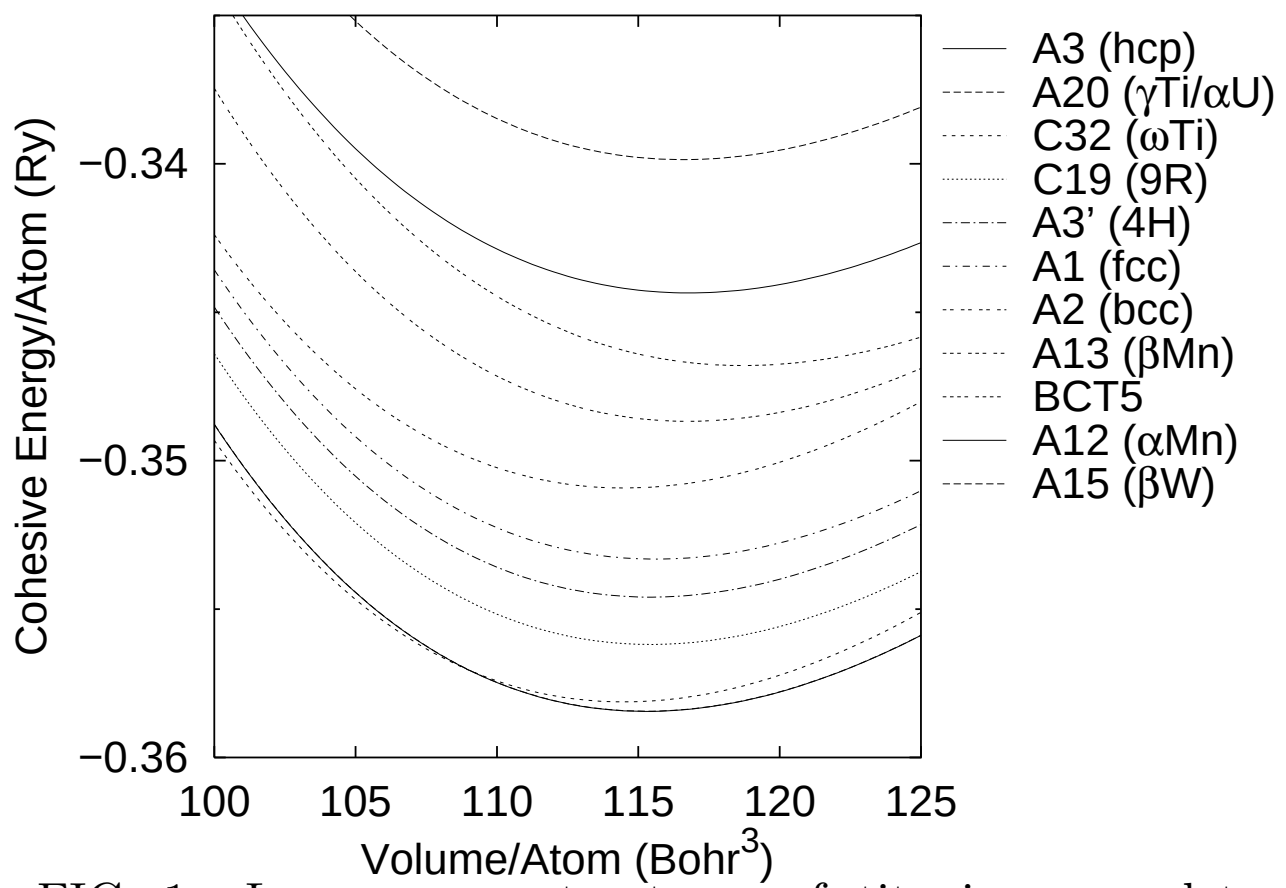

FIG. 1. Low energy structures of titanium, as determined by the tight-binding parameters described in the text. The γTi phase is described in the text. Over this range of volumes it is degenerate with the hcp (A3, or αTi) structure. The crystal structures are described in full at http://cst-www.nrl.navy.mil/lattice.

TABLE II. Elastic constants of αTi at the experimental volume, as determined from the parameters described in the text and compared to experiment. [27] All values are in GPa.

	TB	Exp.		TB	Exp.
C_{11}	127	162	C_{33}	147	181
C_{12}	81	92	C_{44}	45	47
C_{13}	64	69			

TABLE III. High-symmetry **k**-point phonon frequencies (in cm^{-1}) of αTi at the experimental volume, as determined from the parameters described in the text and compared to experiment. [28] The symmetry notation is from Miller and Love. [29,30]

		TB	Exp.			TB	Exp.
Γ_3^+		189	185				
Γ_5^+		141	137	M_1^+	LO	259	257
A_1	LA/LO	178	191	M_2^+	TA	56	113
A_3	TA/TO	98	101	M_2^-	TO	171	202
K_1		275	234	M_3^+	TA	99	127
K_4		180	200	M_3^-	TO	192	232
K_5	LA/LO	144	207	M_4^-	LA	200	234
K_6	TA/TO	141	173				

implies a −5 GPa ωTi-αTi phase transition. We have adjusted our tight binding parametrization to shift the ωTi phase equilibrium upwards by 0.8 mRy/atom. This produces an αTi-ωTi phase transition at 6 GPa, in good agreement with the 9 GPa transition found in Ref. [1] As we shall see, this has important consequences for the ωTi-γTi phase transition.

We have tested the fit in a variety of ways. In Table I we show the equilibrium lattice constants for α-, β- and ωTi, as determined by our tight-binding parameters, our first-principles LAPW calculations, and experiment. [1,26] The TB agreement with experiment is comparable to that achieved by the first-principles calculations.

We also examined the behavior of a variety of crystal structures using our tight-binding parameters. Fig. 1 shows the energy/volume behavior of a number of low energy structures. As expected, the observed phases (αTi and ωTi) are followed by close-packed stacking fault phases (9R, 4H, and fcc), and then other common metallic phases.

We further checked the behavior of our tight-binding Hamiltonian by determining the elastic constants and phonon frequencies in αTi, as shown in Tables II and III, respectively. Compared to experiment, we find an RMS error of 22 GPa for the elastic constants, and 32 cm^{-1} for the phonon frequencies. This is typical of the predictive capability of the tight-binding method for hcp metals. [19]

We studied the α-ω-γ transition path in titanium by fixing the volume of a given phase, and then minimizing the total energy as a function of the other parameters (c/a for α (hcp) and ω; b/a, c/a, and y for γ). The pressure was calculated in one of two ways: by differentiating an extended Birch fit, [31,32] and by calculating the pressure by numerical differentiation of the total energy with respect to volume. The enthalpy of each phase, $H(P) = E + PV$ is then calculated by both methods. In Fig. 2 we show the enthalpy of the ωTi, γTi, and bcc (βTi) phases in the transition region. From the plot we see that the ωTi-γTi phase transition takes place at about 102 GPa, compared to the experimental result of 116 GPa. We also see a γTi-βTi phase transition at about 115 GPa. This is not seen experimentally, but it suggests that we may expect a higher pressure γTi-βTi phase transition, which would complete the α-ω-β transition sequence seen in Zr and Hf, albeit with an interloping γTi phase between ωTi and βTi. More details of the phase transitions predicted by our Hamiltonian are shown in Table IV.

In the absence of the γTi phase, Fig. 2 shows that

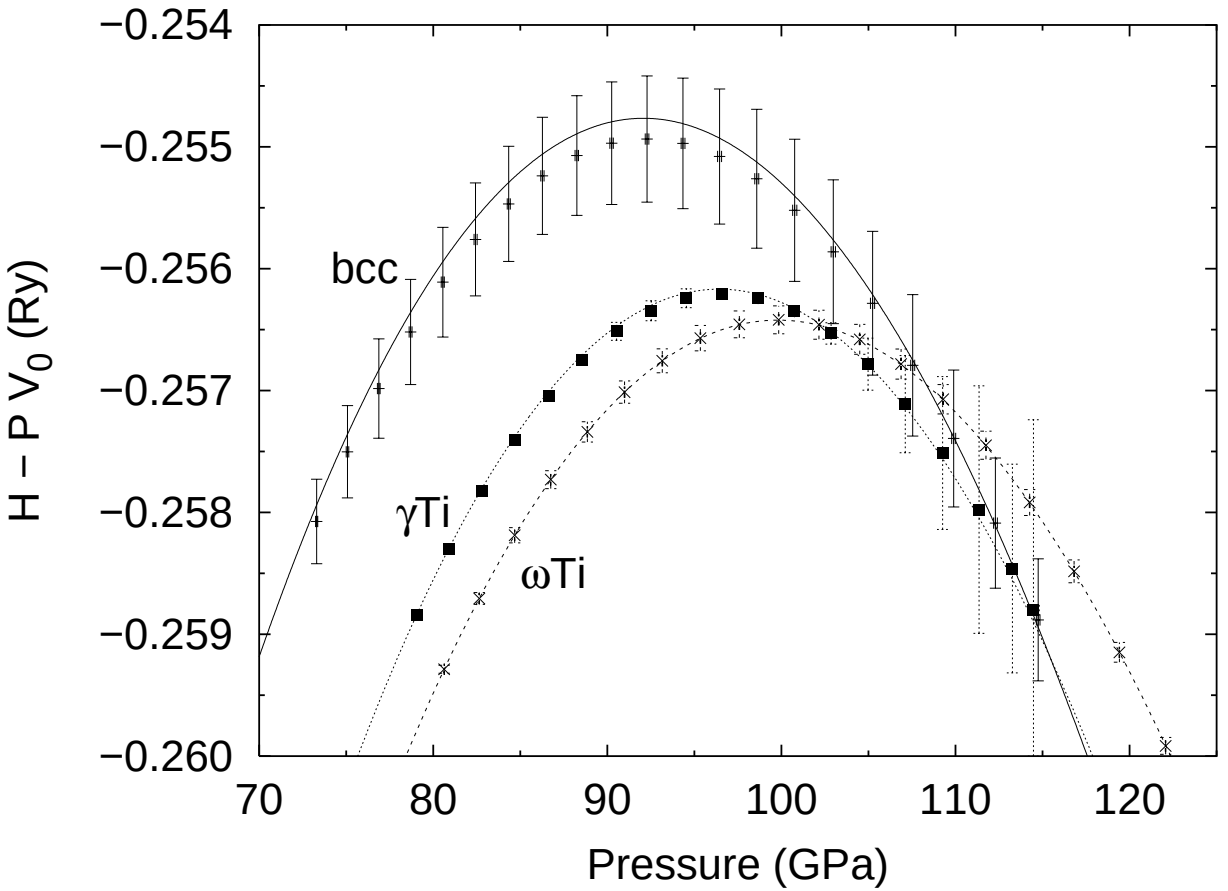

FIG. 2. The enthalpy for several phases of titanium in the ω-γ transition region. For increased clarity we subtract PV_0 from each enthalpy, where the reference volume $V_0 = 75$ Bohr^3. The lines are derived from extended Birch fits [31,32] to the $E(V)$ data for each phase. Numerical differentiation of $E(V)$ provides the pressure for the points, and a check on the accuracy of the Birch fit. The error bars on the points represent estimates of the uncertainty in the energy and pressure calculations due to the numerical k-point integration.

TABLE IV. Pressure induced phase transitions in titanium, as determined by the tight-binding parameters described in the text [25] and compared to experiment. [1].

	TB		Exp.	
Transition	Pressure (GPa)	$\Delta V/V$ (%)	Pressure (GPa)	$\Delta V/V$ (%)
$\alpha \to \omega$	6	-0.6	9	-1.9
$\omega \to \gamma$	102	-1.3	116	-1.6
$\gamma \to \beta$	115	≈ 0	none up to 146 GPa	

there would be an ωTi-βTi phase transition at 110 GPa. This is in good agreement with the prediction made from the LAPW/GGA calculations in our database, 105 GPa, and with the LMTO/GGA prediction of 98 GPa found in Ref. [5].

The behavior of titanium in the α-, β-, and γTi phases is explored further in Fig. 3, which shows the lattice parameters b/a, c/a, and y as a function of the volume. We see that at a volume of about 85 Bohr^3/atom there is an abrupt change from hcp αTi into the lower symmetry γTi phase. From this point the structure merges more or less continuously into bcc βTi at about 70 Bohr^3/atom. Note, however, that none of these phases is observed in the volume range 74-108 Bohr^3, as this is the region where the ωTi phase is stable.

Finally, we note that our LAPW calculations and other first-principles calculations [5–8] place the ωTi phase slightly lower in energy than the αTi phase, leading to a direct transition from ωTi to βTi at 105 GPa. Hence, the essential difference between the first-principles calculations and our TB model is the ordering of the αTi and ωTi phases.

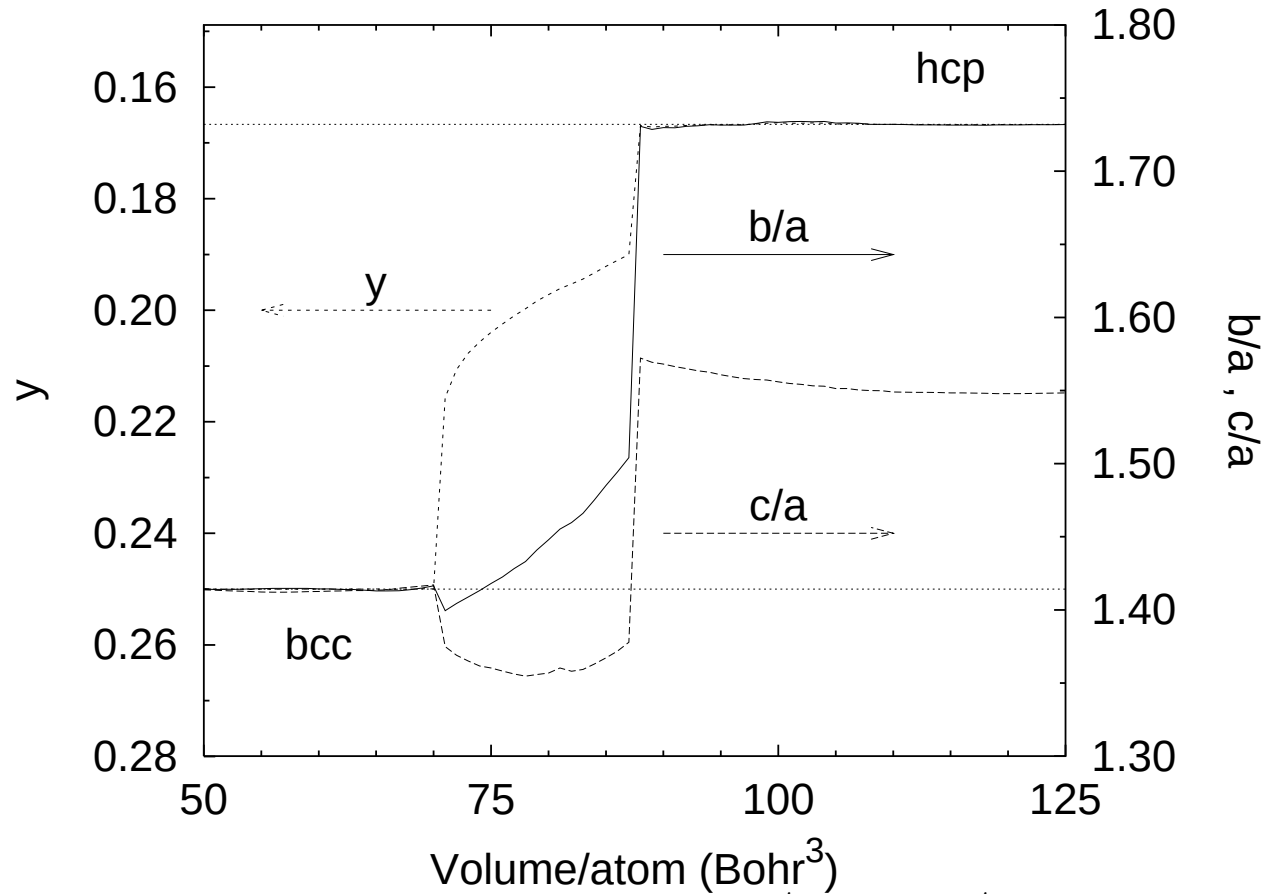

FIG. 3. The lattice parameters b/a and c/a and the internal parameter y which minimize the total energy of γTi as a function volume, using the tight-binding parameters described in the text. The horizontal dotted lines indicate the parameter values needed to achieve an ideal bcc lattice ($y = 1/4$, $b/a = c/a = \sqrt{2}$) and an hcp lattice ($y = 1/6$, $b/c = \sqrt{3}$, arbitrary c/a).

In conclusion, our tight-binding Hamiltonian provides a good description of the low pressure behavior of titanium, and shows the correct α-ω-γ transition sequence as reported in recent experiments. Our work suggests that current first-principles density functional calculations, which place the ωTi phase below the αTi phase, will also fail to predict the stability of the γTi phase under pressure.

We thank I. I. Mazin for reminding us of Ref. [17], and T. A. Adler for pointing us to the αU structure. This work was supported by the U. S. Office of Naval Research. The development of the tight-binding codes was supported in part by the U. S. Department of Defense Common HPC Software Support Initiative (CHSSI).

---

[1] Y. K. Vohra and P. T. Spencer, Phys. Rev. Lett. **86**, 3068 (2001).
[2] S. K. Sikka, Y. K. Vohra, and R. Chidambaram, Prog. Mat. Sci. **27**, 245 (1982).
[3] A. V. Dobromyslov and N. I. Taluts, Physics of metals and metallography **69**, 98 (1990).
[4] H. Xia, G. Parthasarathy, H. Luo, Y. K. Vohra, and A. L. Ruoff, Phys. Rev. B **42**, 6736 (1990).
[5] G. Jomard, L. Magaud, and A. Pasturel, Phil. Mag. B **77**, 67 (1998).
[6] J. S. Gyanchandani, S. C. Gupta, S. K. Sikka, and R. Chidambaram, J. Phys.: Cond. Matt. **2**, 301 (1990).
[7] R. Ahuja, J. M. Wills, B. Johansson, and O. Eriksson,

Phys. Rev. B **48**, 16269 (1993).

[8] C. W. Greeff, D. R. Trinkle, and R. C. Albers, J. Appl. Phys. **90**, 2221 (2001).

[9] S. R. Nishitani, H. K. H, and M. Aoki, Materials Science and Engineering A **312**, 77 (2001).

[10] S. A. Ostanin and V. Y. Trubitsin, Journal of Physics: Condensed Matter **9**, L491 (1997).

[11] H. Xia, S. J. Duclos, A. L. Ruoff, and Y. K. Vohra, Phys. Rev. Lett. **64**, 204 (1990).

[12] H. Xia, A. L. Ruoff, and Y. K. Vohra, Phys. Rev. B **44**, 10374 (1991).

[13] *Binary Alloy Phase Diagrams*, edited by T. B. Massalski (American Society for Metals, Metals Park, Ohio, 1987).

[14] *Pearson's Handbook of Crystallographic Data for Intermetallic Phases*, 2^{nd} ed., edited by P. Villars and L. Calvert (ASM International, Materials Park, Ohio, 1991).

[15] *Strukturbericht*, edited by K. Herrman (Akademische Verlagsgesellschaft Becker & Erler, Leipzig, 1938), Vol. VI.

[16] More information about the αU (A20) structure can be obtained at http://cst-www.nrl.navy.mil/lattice/struk/a20.html.

[17] R. M. Wentzcovitch and M. L. Cohen, Phys. Rev. B **37**, 5571 (1988).

[18] R. E. Cohen, M. J. Mehl, and D. A. Papaconstantopoulos, Phys. Rev. B **50**, 14694 (1994).

[19] M. J. Mehl and D. A. Papaconstantopoulos, Phys. Rev. B **54**, 4519 (1996).

[20] M. J. Mehl and D. A. Papaconstantopoulos, Europhys. Lett. **31**, 537 (1995).

[21] O. K. Andersen, Phys. Rev. B **12**, 3060 (1975).

[22] S.-H. Wei and H. Krakauer, Phys. Rev. Lett. **55**, 1200 (1985).

[23] J. P. Perdew, in *Electronic Structure of Solids '91*, edited by P. Ziesche and H. Eschrig (Akademie Verlag, Berlin, 1991).

[24] J. P. Perdew, J. A. Chevary, S. H. Vosko, , K. A. Jackson, M. R. Pederson, D. J. Singh, and C. Fiolhais, Phys. Rev. B **46**, 6671 (1992).

[25] The titanium parameters discussed in this Letter are available at http://cst-www.nrl.navy.mil/bind/ti.html.

[26] J. Donohue, *The Structures of the Elements* (John Wiley & Sons, New York, 1974).

[27] G. Simmons and H. Wang, *Single Crystal Elastic Constants and Calculated Aggregate Properties: A HANDBOOK*, 2^{nd} ed. (M.I.T. Press, Cambridge, Massachusetts and London, 1971).

[28] C. Stassis, D. Arch, B. N. Harmon, and N. Wakabayashi, Phys. Rev. B **19**, 181 (1979).

[29] S. C. Miller and W. F. Love, *Tables of Irreducible Representations of Space Groups and Co-Representations of Magneticd Space Groups* (Pruett, Bolder, 1967).

[30] H. T. Stokes and D. M. Hatch, *Isotropy Subgroups of the 230 Crystallographic Space Groups* (World Scientific, Singapore, 1988).

[31] F. Birch, J. Geophys. Res. **83**, 1257 (1978).

[32] M. J. Mehl, B. M. Klein, and D. A. Papaconstantopoulos, in *Intermetallic Compounds - Principles and Practice*, edited by J. Westbrook and R. Fleischer (John Wiley and Sons, London, 1994), Vol. 1, Chap. 9, pp. 195–210.